

**NASA  
Technical  
Paper  
3064**

March 1991

**Investigation of  
Microstructural Changes  
in Polyetherether-Ketone  
Films at Cryogenic  
Temperatures by Positron  
Lifetime Spectroscopy**

Jag J. Singh,  
Abe Eftekhari,  
Terry L. St. Clair,  
and Danny R. Sprinkle


(NASA-TP-3064) INVESTIGATION OF  
MICROSTRUCTURAL CHANGES IN  
POLYETHERETHER-KETONE FILMS AT CRYOGENIC  
TEMPERATURES BY POSITRON LIFETIME  
SPECTROSCOPY (NASA) 13 p

N91-18210

CSCL 11D H1/24

Unclas  
0319922

**NASA**



1991

# Investigation of Microstructural Changes in Polyetherether-Ketone Films at Cryogenic Temperatures by Positron Lifetime Spectroscopy

Jag J. Singh  
*Langley Research Center*  
*Hampton, Virginia*

Abe Eftekhari  
*Analytical Services & Materials, Inc.*  
*Hampton, Virginia*

Terry L. St. Clair and Danny R. Sprinkle  
*Langley Research Center*  
*Hampton, Virginia*



National Aeronautics and  
Space Administration  
Office of Management  
Scientific and Technical  
Information Division

The use of trademarks or names of manufacturers in this report is for accurate reporting and does not constitute an official endorsement, either expressed or implied, of such products or manufacturers by the National Aeronautics and Space Administration.

## Abstract

Microstructural changes in polyetherether-ketone (PEEK) films have been investigated in the temperature range of 23°C to -196°C by using positron lifetime spectroscopy. It has been determined that the total free volume decreases by about 46 percent in amorphous PEEK samples and about 36 percent in semicrystalline PEEK samples when they are cooled from room temperature to the temperature of liquid nitrogen. If this trend in reduction of free volume with decreasing temperature continues, as expected, PEEK should be able to withstand cooling to the temperature of liquid hydrogen without any detrimental effect on its diffusivity for liquid hydrogen.

## Introduction

Polyetherether-ketone (PEEK) is a high-temperature thermoplastic polymer with excellent properties for a wide range of demanding applications. When heated above its melting temperature  $T_m$  and then rapidly quenched to ambient or lower temperatures, the polymer can be isolated in its amorphous form, which has a glass transition temperature  $T_g$  of 143°C. Once the amorphous form of the material is exposed to a temperature between  $T_g$  and  $T_m$ , it rapidly transforms to a semicrystalline form, which has a greatly suppressed glass transition temperature. The chemical structure of PEEK is shown in figure 1.

Polyetherether-ketone is a strong candidate for the matrix of the fiber-reinforced composites under consideration for the slush hydrogen fuel tank for the National Aero-Space Plane (NASP). However, there is some concern that PEEK might undergo molecular rearrangements under cryogenic conditions which may result in fuel leakage. Positron lifetime spectroscopy (PLS) has been used to investigate morphological features of PEEK as a function of temperature in the range of 77K to 300K, and the results of these measurements are described herein.

## Symbols

A bar over a symbol indicates an average value.

|                 |  |
|-----------------|--|
| $C$             | microstructural constant   |
| $F$             | $= f_2 + f_3$  |
| $f_2, f_3$      | free-volume fractions associated with second and third lifetime components |
| $I_1, I_2, I_3$ | intensities of first, second, and third lifetime components                |
| $LN_2$          | liquid nitrogen  |

|                          |  |
|--------------------------|--|
| PEEK                     | polyetherether-ketone  |
| $T_g$                    | glass transition temperature, °C                               |
| $T_m$                    | melting temperature, °C  |
| $V_{f2}, V_{f3}$         | free-volume cell size for second and third lifetime components |
| $\tau_1, \tau_2, \tau_3$ | lifetimes of first, second, and third components               |

## Experimental Procedure

Ten-mil-thick PEEK films were obtained from ICI Films, a business subsidiary of ICI Americas, Inc. The as-received films were unoriented, noncrystalline, and transparent. The semicrystalline variety of these films was prepared by heating them to 160°C for 1 hour and allowing them to cool to room temperature. The presence of crystallinity was evidenced by the onset of opacity in the films.

The  $Na^{22}$  positron lifetimes in the test films were measured in order to infer the concentration and size distributions of free-volume cells in them. (See refs. 1 and 2.) Since the single-film thickness (0.25 mm thick) was inadequate to stop the majority of  $Na^{22}$  positrons, the films were folded three times to make test coupons that were 0.75 mm thick, 2.5 cm long, and 2.5 cm wide. The  $Na^{22}$  source foil was sandwiched between two test coupons, and positron lifetime spectra in them were measured by using the standard fast-fast coincidence measurement technique (ref. 3). However, before starting extensive lifetime measurements in the test coupons, spectra were also measured in single 0.25-mm-thick films by using a recently developed (refs. 4 and 5) slow positron beam generator. These spectra were then compared with the lifetime spectra in the 0.75-mm-thick coupons. The results are summarized in table I. It is obvious that the results are in very good agreement. This indicates that the three films in the test coupons are in intimate contact with each other. (Or, at least, the annihilation lifetimes in the noncontact islands (free-volume cells) at the interface are outside the experimental time window of 50 nsec.) After this test, all measurements were made with three-fold test coupons in standard PLS geometry for thick targets, since this arrangement permits easier sample temperature control.

Positron lifetime measurements in both the amorphous and semicrystalline PEEK test coupons were made at a series of decreasing temperatures, beginning with the ambient temperature.

### Amorphous Films

The PLS measurements in as-received PEEK film samples were made at a steady-state temperature of

23°C (room temperature), -12°C, -40°C, -62°C, and -196°C. The -12°C and -40°C measurements were made by using the system illustrated in figure 2, while the -62°C and -196°C measurements were made with the system illustrated in figure 3. The results in amorphous films are summarized in table II.

### Semicrystalline Films

The semicrystalline films were prepared by heating the amorphous films to 160°C and then allowing them to cool to room temperature. No attempt was made to release any thermal stress that may have been induced in the test samples to better simulate real service conditions. Lifetime measurements were made at room temperature before heating the films to 160°C and after cooling them to room temperature. Following room-temperature measurements, lifetime measurements were made at the same temperatures as amorphous films. These results are summarized in table III.

On the basis of lifetime data, the free-volume fraction (ref. 6) associated with microvoids in the PEEK samples has been calculated. The results are summarized in table IV. It is obvious that the total free-volume fraction decreases with decreasing temperature in both phases of the PEEK samples.

### Results and Discussion

The microstructures of the two phases, as well as the effects of temperature on them, are different. For example, the sizes of the two amorphous sample microvoid population groups average about  $9.9 \times 10^{-3} \text{ nm}^3$  and  $8.3 \times 10^{-2} \text{ nm}^3$  at room temperature, whereas the corresponding sizes in the semicrystalline samples are  $1.7 \times 10^{-3} \text{ nm}^3$  and  $8.8 \times 10^{-2} \text{ nm}^3$ . As the sample temperature is lowered from room temperature (23°C) to LN<sub>2</sub> temperature (-196°C), the smaller hole size increases from  $9.9 \times 10^{-3} \text{ nm}^3$  to  $1.2 \times 10^{-2} \text{ nm}^3$  in the amorphous sample, and it goes from  $1.7 \times 10^{-3} \text{ nm}^3$  to  $8.9 \times 10^{-3} \text{ nm}^3$  in the semicrystalline sample. The larger microvoids remain unchanged in size with decreasing temperature in both phases, though their concentrations are drastically reduced. The total free volume associated with both groups of microvoids in both types of samples of PEEK has been calculated. It goes down from 0.50 percent to 0.26 percent in the amorphous samples and from 0.44 percent to 0.28 percent in the semicrystalline samples as the sample temperatures are lowered from room temperature to LN<sub>2</sub> temperature. These results are illustrated in figures 4 to 9.

Several interesting conclusions can be drawn from these figures: (1) The concentration of both types of microvoids decreases with decreasing temperature in both phases of PEEK; (2) The free-volume fraction

associated with larger microvoids decreases, and the fraction associated with smaller microvoids increases, as the sample temperature is lowered; (3) There is a net decrease in total free-volume fraction with decreasing temperature in both phases of PEEK. The last two conclusions indicate that some of the larger microvoids disappear altogether, whereas a smaller fraction of them reappear as intermediate-sized microvoids.

From the preceding discussion, it appears that PEEK undergoes conformational changes when its temperature is lowered. However, these conformational changes appear to reduce the free-volume fraction in the material and therefore make it less likely to suffer deleterious effects on its diffusivity for hydrogen when cooling to LH<sub>2</sub> temperature.

### Concluding Remarks

The morphology of amorphous and semicrystalline polyetherether-ketone (PEEK) samples has been investigated at a number of temperatures in the range of 23°C to -196°C. Free-volume fraction in PEEK decreases as its temperature is lowered to that of liquid nitrogen (LN<sub>2</sub>). Consequently, PEEK should not suffer any adverse effects on its diffusivity for hydrogen when exposed to LH<sub>2</sub> temperature if, as expected, the trend in reduction in free volume with decreasing temperature continues.

NASA Langley Research Center  
Hampton, VA 23665-5225  
February 7, 1991

### References

1. Eldrup, Morten: On Positron Studies of Molecular Crystals. *Positron Annihilation*, Paul G. Coleman, Suresh C. Sharma, and Leonard M. Diana, eds., North-Holland Publ. Co., 1982, pp. 753-762.
2. Nakanishi, H.; and Jean, Y. C.: Positrons and Positronium in Liquids. *Positron and Positronium Chemistry*, D. M. Schrader and Y. C. Jean, eds., Elsevier Science Publ. Co., Inc., 1988, pp. 159-192.
3. Singh, Jag J.; Mall, Gerald H.; and Sprinkle, Danny R.: *Analysis of Positron Lifetime Spectra in Polymers*. NASA TP-2853, 1988.
4. Singh, Jag J.; Eftekhari, Abe; and St. Clair, Terry L.: *A Slow Positron Beam Generator for Lifetime Studies*. NASA TM-101590, 1989.
5. Singh, Jag J.; Eftekhari, Abe; and St. Clair, Terry L.: Low Energy Positron Flux Generator for Lifetime Studies in Thin Films. *Nucl. Instrum. & Methods Phys. Res.*, vol. B53, Mar. 1991.
6. Nakanishi, H.; Jean, Y. C.; Smith, E. G.; and Sandreczki, T. C.: Positronium Formation at Free-Volume Sites in the Amorphous Regions of Semicrystalline PEEK. *J. Polymer Sci., Pt. B: Polymer Phys.*, vol. 27, no. 7, 1989, pp. 1419-1424.

Table I. Comparison of Lifetime Data in Single and Three-Fold PEEK Films at Room Temperature

| Single-layer film; positron beam measurement |                                |                                | Triple-layer film; conventional lifetime measurement |                                |                                |
|--|--------------------------------|--------------------------------|--|--------------------------------|--------------------------------|
| $\tau_1/I_1$ ,<br>psec/percent               | $\tau_2/I_2$ ,<br>psec/percent | $\tau_3/I_3$ ,<br>psec/percent | $\tau_1/I_1$ ,<br>psec/percent                       | $\tau_2/I_2$ ,<br>psec/percent | $\tau_3/I_3$ ,<br>psec/percent |
| 274±6/52±2                                   | 561±23/25±3                    | 1841±21/23±2                   | 268±8/51±1   | 569±19/26±2                    | 1823±27/23±2                   |

Table II. Summary of Results in Amorphous PEEK at Various Temperatures

| Temperature <sup>a</sup> , °C | $\tau_1/I_1$ ,<br>psec/percent | $\tau_2/I_2$ ,<br>psec/percent | $\tau_3/I_3^b$ ,<br>psec/percent |
|-------------------------------|--------------------------------|--------------------------------|----------------------------------|
| 23                            | 278±11/53±3                    | 589±39/25±2                    | 1854±30/22±2                     |
| -12                           | 312±8/68±2                     | 825±32/17±2                    | 1854±30/15±1                     |
| -40                           | 344±9/76±2                     | 858±25/10±2                    | 1854±30/14±1                     |
| -62                           | 381±8/75±2                     | 850±40/10±2                    | 1854±30/15±1                     |
| -196                          | 334±8/79±2                     | 879±38/11±2                    | 1854±30/10±1                     |

<sup>a</sup>Temperature errors are ≤1°C.

<sup>b</sup>Ortho-positronium lifetime has been held constant at room-temperature average value of 1854±30 psec, since its value at different temperatures changes by less than experimental error.

Table III. Summary of Results in Semicrystalline PEEK at Various Temperatures

| Temperature <sup>a</sup> , °C | $\tau_1/I_1$ ,<br>psec/percent | $\tau_2/I_2$ ,<br>psec/percent | $\tau_3/I_3^b$ ,<br>psec/percent |
|-------------------------------|--------------------------------|--------------------------------|----------------------------------|
| 23                            | 290±5/57±2                     | 616±22/25±2                    | 1914±19/18±1                     |
| -14                           | 275±9/65±2                     | 596±33/21±2                    | 1914±19/14±1                     |
| -35                           | 310±12/67±2                    | 643±38/20±2                    | 1914±19/13±1                     |
| -60                           | 316±10/70±2                    | 675±38/17±2                    | 1914±19/13±1                     |
| -196                          | 328±9/77±2                     | 803±28/13±2                    | 1914±19/10±1                     |

<sup>a</sup>Temperature errors are ≤1°C.

<sup>b</sup>Ortho-positronium lifetime has been held constant at room-temperature average value of 1914±19 psec, since its value at different temperatures changes by less than experimental error.

Table IV. Comparison of Microvoid Sizes of Amorphous and Semicrystalline Samples of PEEK at Various Temperatures

[Errors in  $f_2$ ,  $f_3$ , and  $F$  are  $\leq 5$  percent]

| Temperature,<br>°C     | Small microvoids               |                      | Large microvoids               |                      | Total free volume <sup>c</sup> ,<br><i>F</i> , percent |
|------------------------|--------------------------------|----------------------|--------------------------------|----------------------|--|
|                        | $\tau_2/I_2$ ,<br>psec/percent | $f_2^a$ ,<br>percent | $\tau_3/I_3$ ,<br>psec/percent | $f_3^b$ ,<br>percent |  |
| Amorphous sample       |                                |                      |                                |                      |  |
| 23                     | 589/25                         | 0.01                 | 1854/22                        | 0.49                 | 0.50   |
| −12                    | 825/17                         | .04                  | 1854/15                        | .35                  | .39  |
| −40                    | 858/10                         | .04                  | 1854/14                        | .33                  | .37  |
| −62                    | 850/10                         | .03                  | 1854/15                        | .34                  | .37  |
| −196                   | 879/11                         | .04                  | 1854/10                        | .23                  | .27  |
| Semicrystalline sample |                                |                      |                                |                      |  |
| 23                     | 616/25                         | 0.01                 | 1914/18                        | 0.43                 | 0.44   |
| −14                    | 596/21                         | .01                  | 1914/14                        | .34                  | .35  |
| −35                    | 643/20                         | .01                  | 1914/13                        | .32                  | .33  |
| −60                    | 675/17                         | .02                  | 1914/13                        | .32                  | .34  |
| −196                   | 803/13                         | .04                  | 1914/10                        | .24                  | .28  |

<sup>a</sup>Free-volume fraction  $f_2 = CI_2V_{f2}$

<sup>b</sup>Free-volume fraction  $f_3 = CI_3V_{f3}$

<sup>c</sup>The constant  $C$  has been obtained by equating  $F = f_2 + f_3$  to the reported value of saturation moisture pickup in PEEK (amorphous).



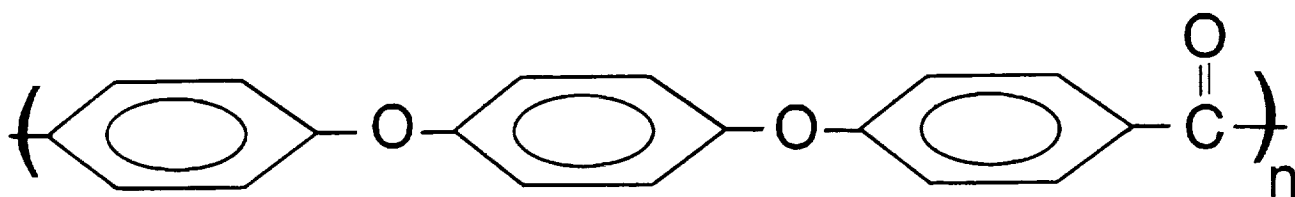


Figure 1. Chemical structure of PEEK.

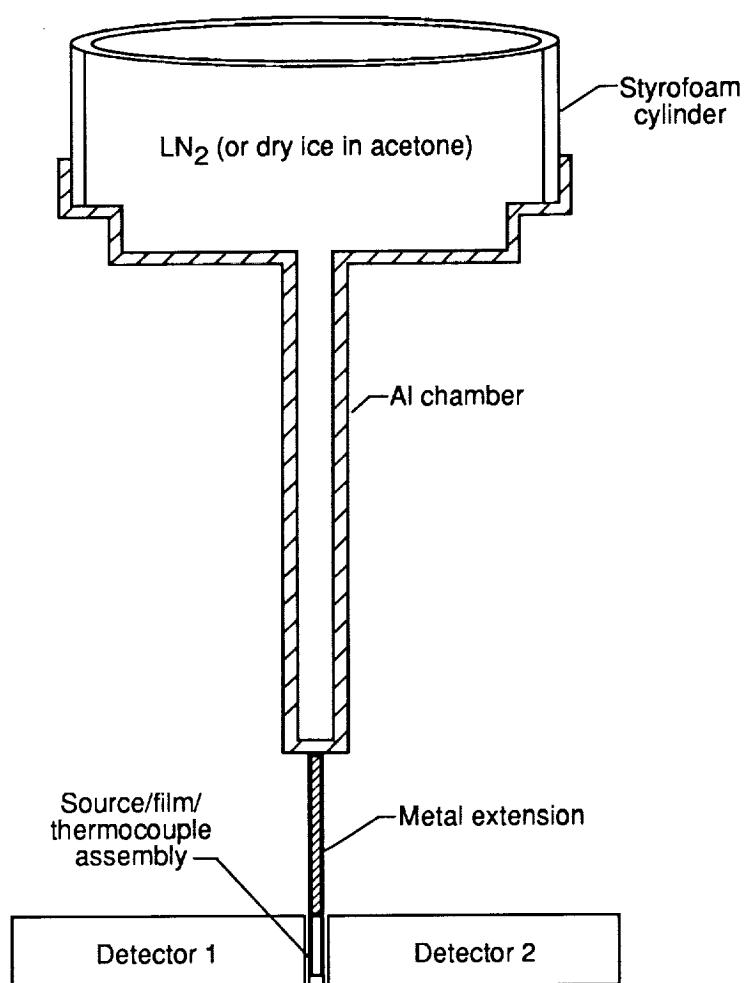


Figure 2. Schematic diagram of sample assembly for lifetime measurements at  $-12^{\circ}\text{C}$  and  $-40^{\circ}\text{C}$ .

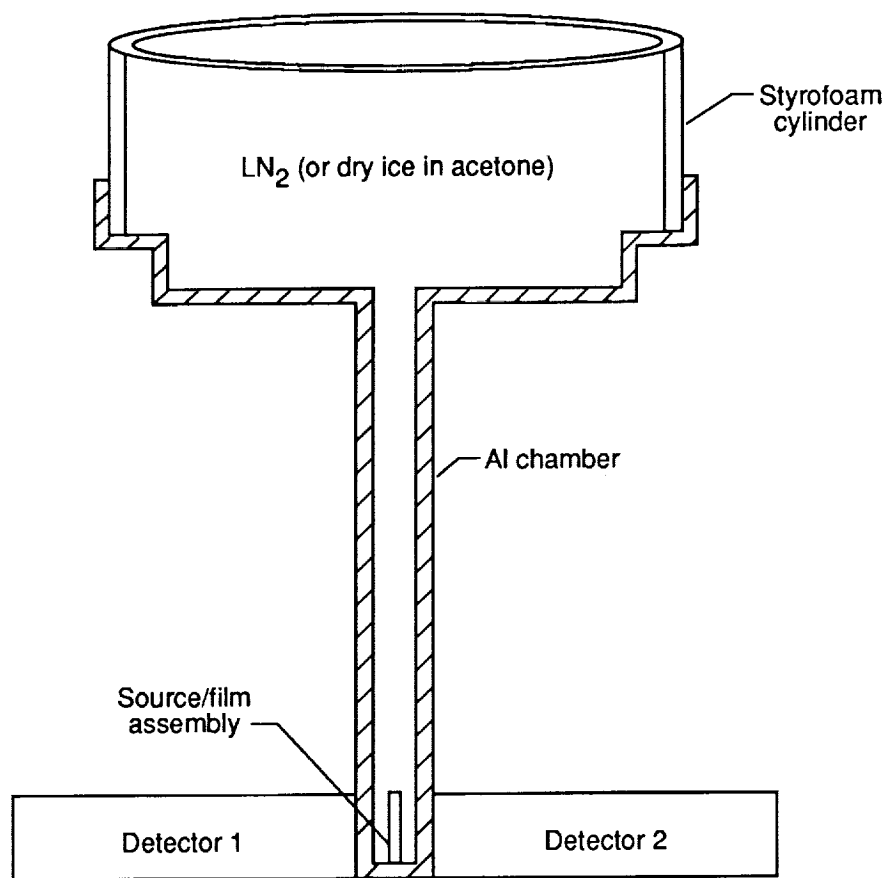


Figure 3. Schematic diagram of sample assembly for lifetime measurements at  $-62^{\circ}\text{C}$  and  $-196^{\circ}\text{C}$ .

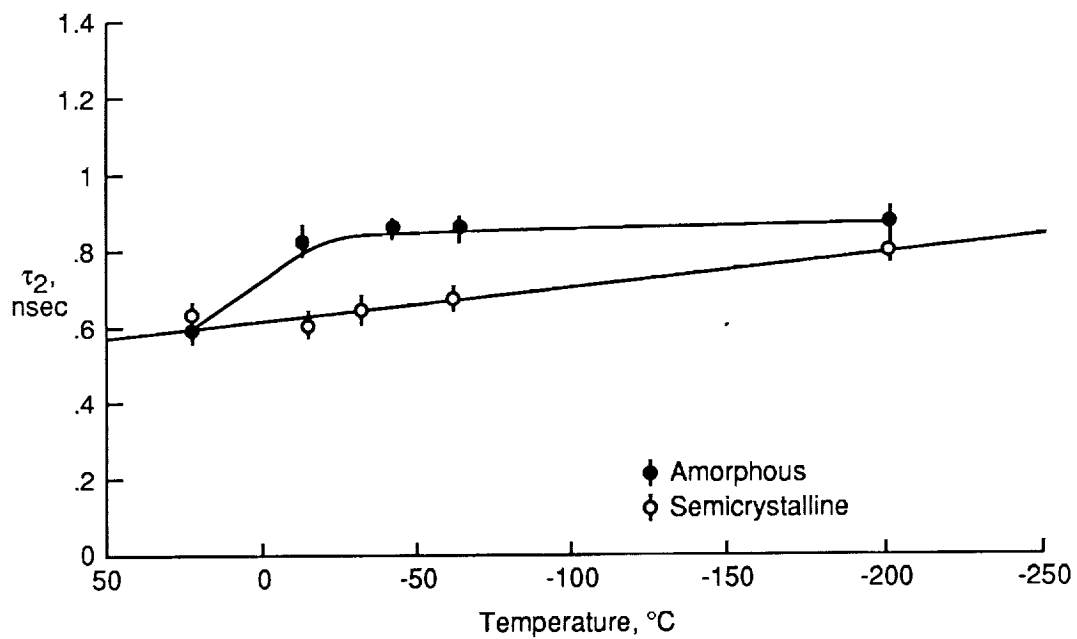


Figure 4. Second-component lifetime versus temperature in PEEK samples.

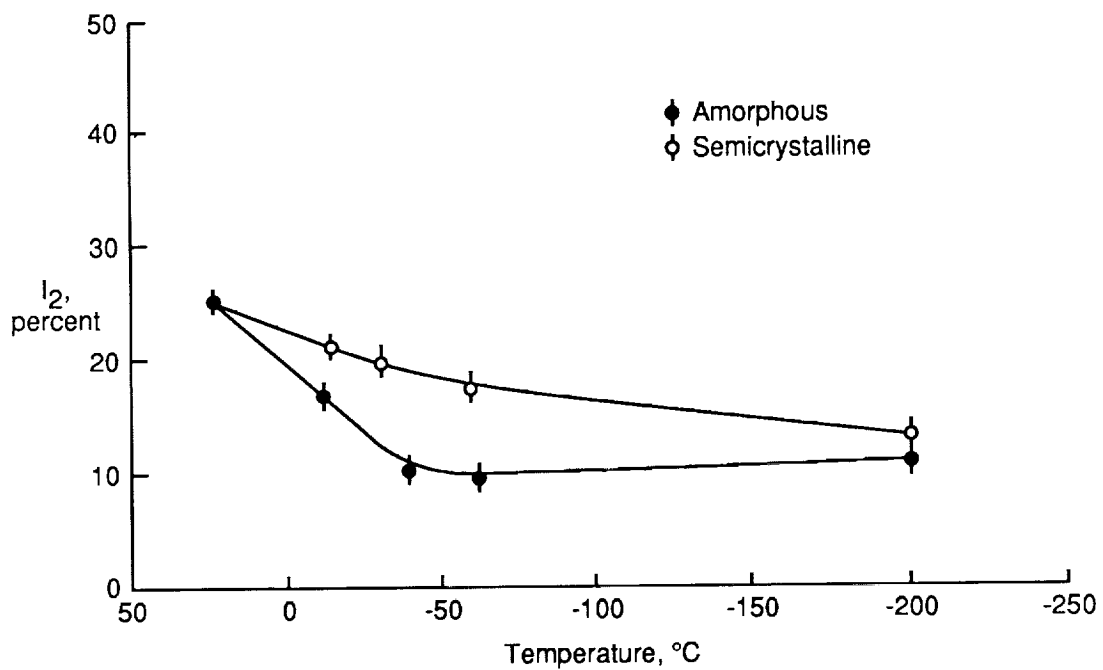


Figure 5. Second-component intensity versus temperature in PEEK samples.

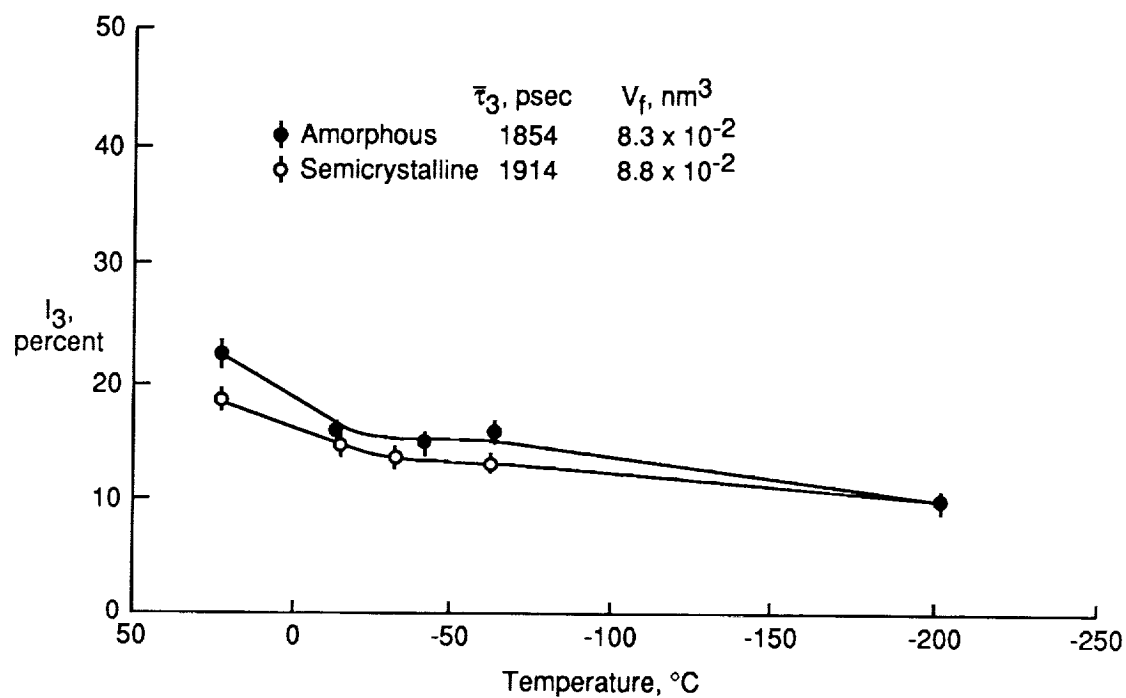


Figure 6. Third-component intensity versus temperature in PEEK samples.

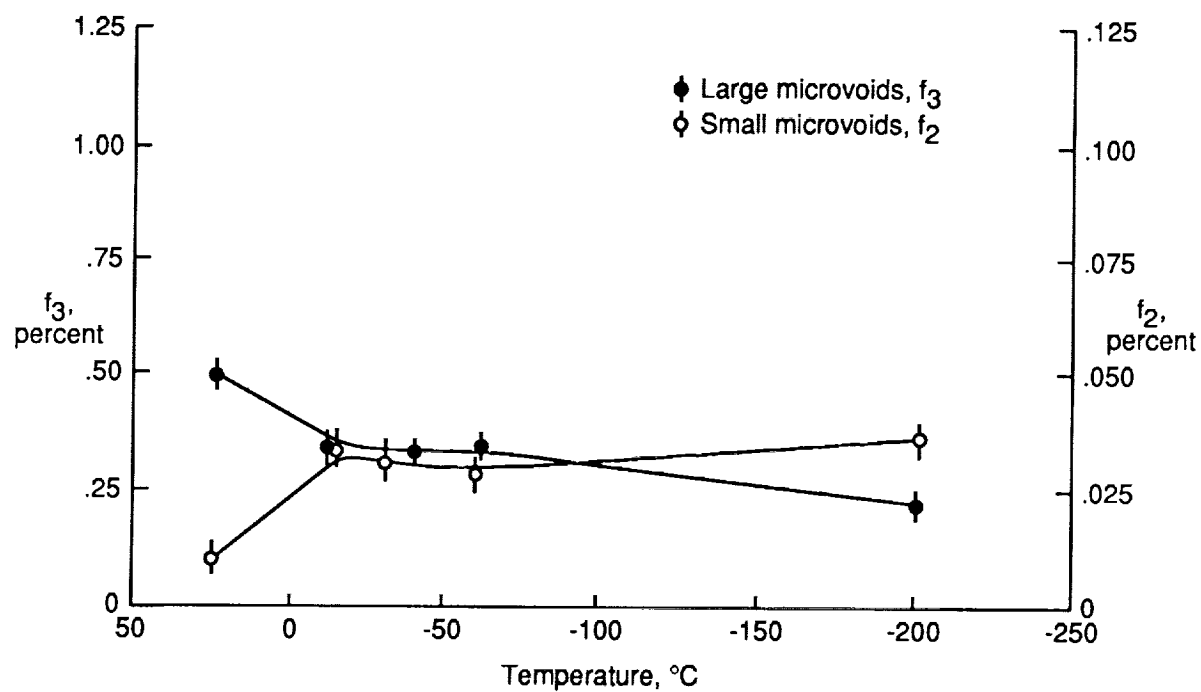


Figure 7. Microvoid fraction versus temperature in amorphous samples.

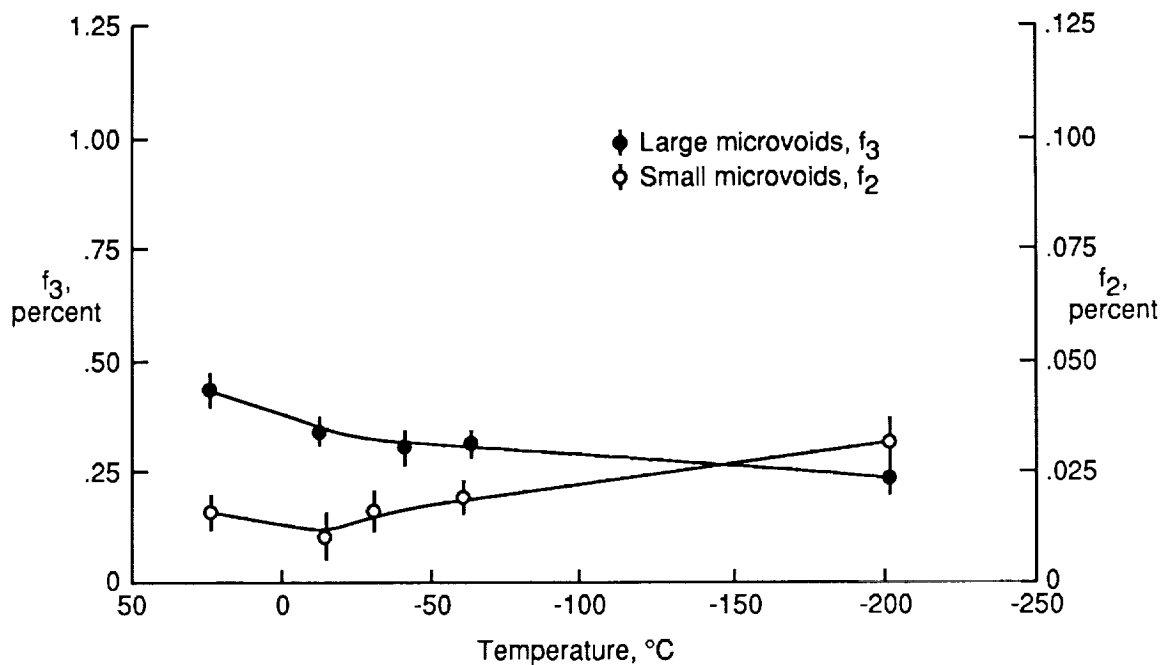


Figure 8. Microvoid fraction versus temperature in semicrystalline samples.

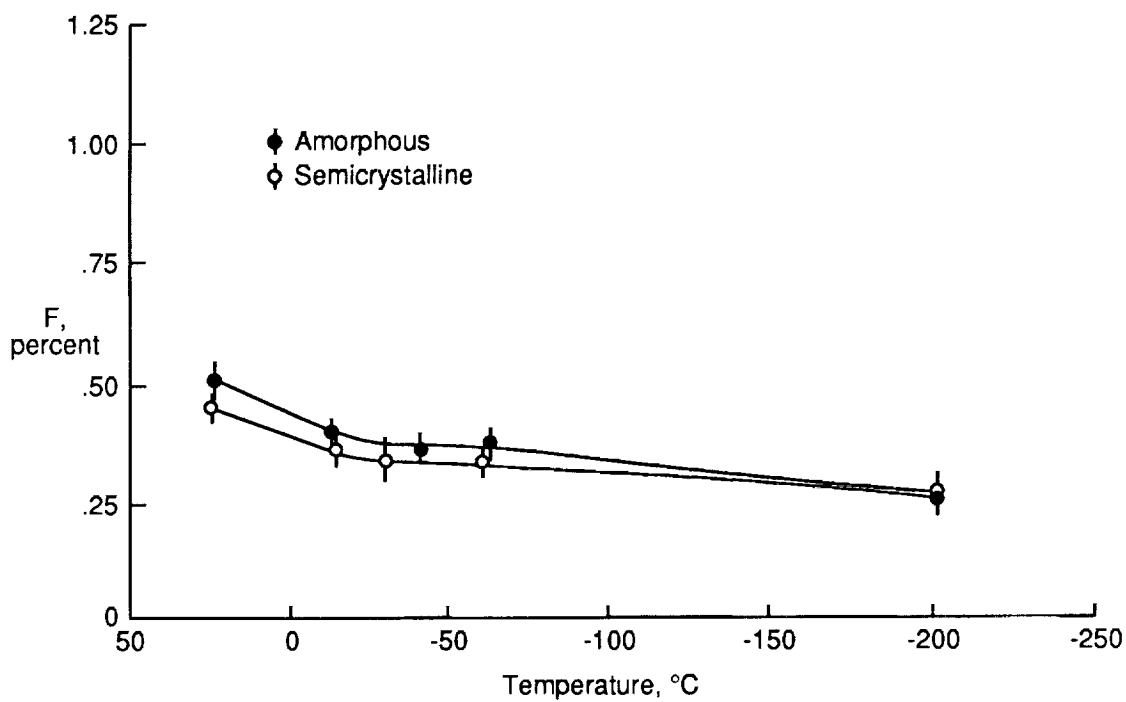


Figure 9. Total free-volume fraction versus temperature in PEEK samples.



# Report Documentation Page

|   |  |  |  |   |  |
|---|--|--|--|---|--|
| 1. Report No.<br>NASA TP-3064   |  | 2. Government Accession No.                          |  | 3. Recipient's Catalog No.  |  |
| 4. Title and Subtitle<br>Investigation of Microstructural Changes in Polyetherether-Ketone Films at Cryogenic Temperatures by Positron Lifetime Spectroscopy  |  |  |  | 5. Report Date<br>March 1991  |  |
|   |  |  |  | 6. Performing Organization Code   |  |
| 7. Author(s)<br>Jag J. Singh, Abe Eftekhari, Terry L. St. Clair, and Danny R. Sprinkle  |  |  |  | 8. Performing Organization Report No.<br>L-16841                                |  |
|   |  |  |  | 10. Work Unit No.<br>506-43-21-05   |  |
| 9. Performing Organization Name and Address<br>NASA Langley Research Center<br>Hampton, VA 23665-5225   |  |  |  | 11. Contract or Grant No.   |  |
|   |  |  |  | 13. Type of Report and Period Covered<br>Technical Paper                        |  |
| 12. Sponsoring Agency Name and Address<br>National Aeronautics and Space Administration<br>Washington, DC 20546-0001  |  |  |  | 14. Sponsoring Agency Code  |  |
|   |  |  |  |   |  |
| 15. Supplementary Notes<br>Jag J. Singh, Terry L. St. Clair, and Danny R. Sprinkle: Langley Research Center, Hampton, Virginia.<br>Abe Eftekhari: Analytical Services & Materials, Inc., Hampton, Virginia.   |  |  |  |   |  |
| 16. Abstract<br>Microstructural changes in polyetherether-ketone (PEEK) films have been investigated in the temperature range of 23°C to -196°C by using positron lifetime spectroscopy. It has been determined that the total free volume decreases by about 46 percent in amorphous PEEK samples and about 36 percent in semicrystalline PEEK samples when they are cooled from room temperature to the temperature of liquid nitrogen. If this trend in reduction of free volume with decreasing temperature continues, as expected, PEEK should be able to withstand cooling to the temperature of liquid hydrogen without any detrimental effect on its diffusivity for liquid hydrogen. |  |  |  |   |  |
| 17. Key Words (Suggested by Author(s))<br>Polyetherether-ketone (PEEK)<br>Cryogenic temperatures<br>Microstructural changes<br>Positron lifetime spectroscopy<br>Free-volume fraction<br>Liquid hydrogen diffusion  |  |  |  | 18. Distribution Statement<br>Unclassified—Unlimited<br><br>Subject Category 24 |  |
| 19. Security Classif. (of this report)<br>Unclassified  |  | 20. Security Classif. (of this page)<br>Unclassified |  | 21. No. of Pages<br>12  |  |
|   |  |  |  | 22. Price<br>A02  |  |